

An Optimal Process Parameters prediction model for Wire Bonding of Ultra-Thin CSP Package Based on Hybrid Methods of Artificial Intelligence

¹Dr. Y. H. Hung, ¹Prof. M. L. Huang, ²C. H. Chang, and ¹Jian-Ting Lin

¹Department of Industrial Engineering & Management
National Chin-Yi University of Technology, Taichung, Taiwan, R. O. C.

hys502@ncit.edu.tw

²Siliconware Precision Industries Co., Ltd.
No.153, Sec. 3, Chung-Shan Rd. Tantz, Taichung, Taiwan, R. O. C.

ABSTRACT

This research combined the Taguchi method and artificial intelligence methods, used them as the prediction tool in wire bond designing parameters for an Ultra-Thin CSP package, and then constructed a set of the optimal parameter analysis flow and steps. This paper employed desirability function to integrate two quality characteristics (loop height and wire pull strength) into a single quality indicator to construct a well-trained neural network prediction model with hybrid genetic algorithm, thereby achieving the objective of improving process yield and robustness design of micro HDD driver IC. The engineers could quickly obtain the optimal production process parameter with the demand of multi-quality characteristics, and enhance the assembly quality and yield of driver IC of micro HDD

Keywords: Multi-quality Characteristics, Desirability Function, Hybrid Genetic Algorithm, Lower Wire Loop.

1.0 Introduction

In IC packaging patterns, gold wire package is one of the main packaging technologies at present, occupying about 90% of the total demand. The wire bonding process is mainly used to transmit signals among components. For the IC package products with a high unit price, the quality of wire bonding process has the greatest effect on the post-process and the yield loss of products, occupying about 40% (Su & Chiang, 2003). In recent years, the portable electronic communication products become increasingly thinner, which makes IC chip package body thinner as well. Meanwhile, the demand for the stacked die package, such as chip scale package (CSP) and wafer level package (WLP) micro package technology are have gradually matured. Thus, IC package manufacturers in Taiwan, in designing new products, have to develop the processing technology and the production flow for new products to satisfy the demands of customers for the design specifications of products. Nowadays, with the increase of the demand for the consumptive digital equipment market, the high-capacity micro HDD (larger than 20 GB) has become the main storage media of the portable digital products. Driver IC is the key electronic component of micro HDD. Driver IC functions as anti-mechanical shock and read head control, and driver IC is responsible of the performance and effectiveness of micro HDD. To satisfy the design of thinner, smaller and low profile of micro HDD, the vertical dimension of driver IC becomes thinner and thinner. This study focuses on the vertical dimension of driver IC in the specification of 0.65mm. There are two chips in the driver IC: ASIC die is for logical control and memory die is responsible for read-and-write for buffer memory. There are 180 I/O leads in the CSP package, and the structure includes mold compound, silicon die, rigid substrate and copper trace materials, where the substrate also serves as the connection between die and motherboard. The die is the signal generator and it controls all activity for the device. In other words, the CSP technology is being developed to achieve miniaturized packaging systems with improved space limitations. The advantages to using a CSP over direct chip attach (DCA) include: easier handling, more protection for the chip, simpler board assembly and reduced total package costs (Baliga 1998).

The main assembly sizes of micro HDD driver IC are shown in Fig. 1. The symbols D1, D2, D3, D4, D5 and D6 respectively stand for the top space from gold wire to the border of components, the distance between gold wire and silicon chip, die thickness, die Attach thickness, mold compound thickness and Substrate thickness. Each package should be controlled in tight tolerance. Otherwise, it will be a micro HDD assembly issue. A vertical dimension (Z-axis) control of driver IC is crucial owing to the limited space in micro HDD. In addition, the mold thickness is one of the key materials and it is the major dimension to keep the overall package height ("D5" dimension in Fig. 1). The second key material dimension is substrate thickness and it is a very importance process control item for the CSP assembly,

under cost constrains, this study uses a rigid substrate carrier and it's material dimension specification is 150 μm . ("D6" dimension in Fig. 1).

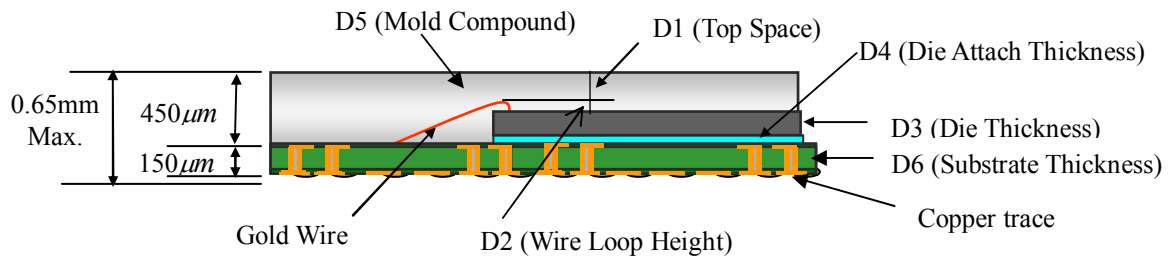


Fig. 1 CSP Packaging Structure for Micro HDD Driver IC

Although the total thickness of driver IC package body is 0.65mm, D5 (the Mold compound thickness) is only 450 μm for assembly space. If the die thickness (125 μm) and die attach thickness (30 μm) are also considered, the distance from the chip to the upper edge of the package body is only 295 μm (D1+D2). However, in the present CSP packaging process, the height of gold wire is usually designed as 130~200 μm . Thus the space from the upper edge of gold wire to the outer side of package body becomes smaller (D1). Especially, after the Molding process, because of the effect of warpage, gold wire is exposed out of package body, which would influence the assembly yield rate. In order to avoid this situation, we have to design the gold wire height of driver IC wire bonding process (D2) as 60~100 μm . In order to satisfy the demand in design and take the quality of bonding process into consideration, in this study, the loop height specification ($60\pm 15\mu\text{m}$) and the gold wire pull strength (over 2 gf) were defined as two key quality characteristics. In this study, the Taguchi method of parameter design using the static characteristic was employed for the robust design of CSP on a substrate carrier with less than 0.65 mm package height. And to probe into the overall output performance of lower loop processes, this paper to construct a well-trained neural network prediction system with hybrid genetic algorithm (HGA).

2.0 Literature Review

In previous researches on wire bonding process, the parameters used to measure the loop height and the quality characteristic of wire bonding process include: ball height, ball size, pull strength, shear strength, the height of heat affected zone (HAZ). The so-called height of HAZ refers to the area where the structure changes because the wire bonding is heated, after the process of Electrical Flame-off (EFO). In fact, wire bonding loop height has a close connection with wire bonding loop process technology, while the forming of wire bonding is mainly affected by the materials and looping parameters of wire bonding. Therefore, proper looping parameters can not only effectively reduce the loop height, but also increase the reliability of wire bonding quality (Hu et al., 1995; Ohno et al., 1991).

The previous researches on the forming of gold wire track, loop height and gold wire strength showed that the control factors affecting the quality of wire bonding included: gold wire (its shape, materials, length, and radius), discharge strength (the length of heat affected zone), the design of lead frame (leads' width, thickness and length), the materials of lead frame, shape of wire loop (the width and length of wire loop, turns and the position of turn), the pull wire parameters of wire bonder etc. The correlative process parameters are: wire bonder, types of bonding probe, temperature of wire bonding, time of wire bonding, bonding force, bonding speed, ultrasonic power, bonding time, free air ball size, loop length, loop height etc. (Chen & Lin 2000; Tsao 2000; Su & Chiang, 2003). The widely-used statistical research methods are: Experimental of Design (DOE) (Groover et al., 1994), Response Surface Methodology (RSM) (Shu 1992), finite element method (FEM) (Liu & Chao et al., 2004; Chaudhr 1998) and Taguchi method (Chen 2000). Taguchi developed procedures that apply orthogonal arrays of statistically designed experiments to efficiently obtain the best model with the fewest possible experiments. However, most Taguchi procedures have been applied to analyzing only linear systems under the assumption of the addition of individual factor effects (Tong, Su, & Wang, 1997). In other words, the Taguchi method is not a panacea to all parameter design problems. Some scholars advised to solve this problem with RSM, but RSM could not completely solve the problems with multi-quality characteristics.

In recent years, artificial neural networks (ANNs) have been developed to mimic the behavior of biological neural nets, and have successfully solved problems through generalization of a limited quantity of training data, overall trends in functional relationships (Sandro 2000; Schalkoff 1997). ANNs have been used in a wide range of applications and proven to be effective in performing complex functions in

various fields. ANNs can be constructed to perform classification (Raimundo & Narayanaswamy 2001), approximate equations (Joo et al., 2001), and predict values (Kim et al., 2005; Su & Chiang 2003). In predictive modeling, the objective is to map a set of input patterns onto a set of output patterns. In recent years, many researches have been conducted based on the Taguchi-neural network for electronic packages and in predicting the wire bond quality characteristics (Chen & Lin 2000; Lo & Tsao 2002; Tsao 2000). Through the use of the Taguchi-neural network model, the prediction model between IC wire bond process parameters and multiple quality characteristics was generated (Su & Chiang 2003). However, building an optimal prediction model with multiple quality characteristics is complicated by the presence of many training factors. Training factors typically involved in building a Taguchi-neural network model may include: the hidden neuron, training tolerance, initial weight distribution, and function gradient. The most difficulty problem often arises from the nature of randomness in the initial weight distribution (Kim et al., 2001). GA is widely used to search for optimized parameters to satisfy given constraints (Goldberg, 1989). The advantage of the GA approach is that it can handle arbitrary kinds of constraints and objectives.

3.0 Prediction Model of Multi-quality Characteristics

This section is to build the experimental factors of wire bonding of driver IC through the Taguchi method and construct two importance quality characteristics. Next, the levels of experimental factors are normalized as the predict variables for wire bonding neural network (WBNN), and the loop height and pull strength from Taguchi experiments are set as the output of WBNN to construct the non-linear network models. The WBNN is evaluated and selected with respect to the root mean-squared error (RMSE) functions. Then, the optimal prediction model of WBNN is obtained by HGA.

3.1.1 Taguchi Experiment Design

Conventionally, engineers apply the Taguchi method to conduct parameter design in a variety of industrial practices. The Taguchi experiments have been successfully applied on the optimum design of IC packages processes. Orthogonal arrays have been developed to accomplish experiment designs with a number of arrays. This method using signal-to-noise ratios (*SN* ratio) takes both the mean and the variability into account. The orthogonal arrays are designated by the notation *L* (*L* for Latin squares) with a subscript, the *SN* ratio (η) is an index of robustness in experimental processing, and the definition of *SN* ratio for STB and LTB response are as follows.

$$\text{Smaller the better: } SN_{STB} = -10\log_{10}(MSD) = -10\log_{10}\left(\frac{1}{n} \sum_{i=1}^n y_i^2\right) \quad (1)$$

$$\text{Larger the better: } SN_{LTB} = -10\log_{10}(MSD) = -10\log_{10}\left(\frac{1}{n} \sum_{i=1}^n \frac{1}{y_i^2}\right) \quad (2)$$

where y_i is the *i*th observation and *n* is the number of observation in each combination and *s* is the deviation of all observations in each combination, respectively. According to the definition of *SN* ratio in Taguchi method (Phadke, 1989), the larger *SN* ratio means the better product quality with less product loss. In the study, twenty-seven trails are conducted by a well-structured orthogonal array $L_{27}(3^{10})$ to attain lower loop height and bounding pull strength. The ten control factors included in Taguchi experiments are power, search speed, EFO current, search height, loop angle, main heat, torch time, loop speed, bond time and bond force. For each parameter, three levels are chosen to cover the range of interest. The control factors with chosen levels are listed in Table 3.

Table 3: The control factors with three levels for the Taguchi experiment

Control factors	Variables	Level		
		1	2	3
Power (mA)	A	60	70	80
Search speed (mil/ms)	B	5	10	15
EFO current (mA)	C	32	45	60
Search height (mil)	D	4	5	6
Loop angle (deg)	E	8	12	16
Main heat (°C)	F	150	155	160
Torch time (ms)	G	1	3	5
Loop speed (um/sec)	H	20	30	40

Bond time (ms)	J	35	37	40
Bond force (mg)	K	9	10	12

3.1.2 Hybrid Genetic Algorithm

In the HGA phase, there are two separate stages: to building a wire bound neural network (WBNN) and then to construct an optimal prediction model of WBNN. First, we choose to use NNs method to building a WBNN because it handles nonlinearity associated with the data well. The widely used algorithms of NN in approximate model are the back propagation neural networks (BPNNs). BPNNs have accomplished this task by learning from a series of data sets related to the system and then applying what was learned to approximate or predict the corresponding output. Processing elements (PEs) are the neurons in a BPNN. The most successful BPNN learning model till now is the least mean square (LMS) algorithm, due to its high prediction accuracy having been excellently proven. Main components of information processing in the neural networks are: inputs, weights, summation function (weighted average of all input data going into a processing element (PE)), transformation function and outputs. In this study, we employ a three-layered BPNN that includes an input layer, a hidden layer and an output layer to construct the WBNN prediction model. Example of steps involving WBNN process is as follows:

1. The input layer, the levels of experimental factors are normalized by Eq. (1) to be served as the predict variables for WBNN.

$$V_{new} = \left[\frac{V_{old} - \mu}{\sigma} \right] \quad (3)$$

where μ is the mean and σ is the standard deviation of the training set. It normalizes the inputs and targets so that they will have zero mean and unity standard deviation.

2. The hidden layers of neurons with nonlinear activation functions (tan-sigmoid) allow the network to learn nonlinear relationship, and the output layer provides the response (loop height and pull strength) of the WBNN to the activation patterns applied to the input layer.
3. The LMS algorithm is employed, and 80% observations are used for training and remaining 20% observations are used for testing.
4. The WBNN are evaluated and selected with respect to the RMSE functions as follows:

$$RMSE = \sqrt{\frac{\sum_{p=1}^m \sum_{j=1}^n (T_j^p - Y_j^p)^2}{m \times n}} \quad (4)$$

where m is the number of test sample, n is the number of neuron, the T_j^p and Y_j^p represent the desired and calculated outputs of the j th output neuron for the p th test sample. The WBNN simulation was performed using MATLAB® software.

GA is a function-related optimization tool most commonly used to resolve the problem of solution space and calculate global optimal solution. So, it is a method of searching target function limit. Though GA is a random search mode, it often searches and amends space to generate reasonable solutions according to cumulative information of every generation of population. During optimization process of GA, possible solution chromosome is composed of genes. In general, every gene is represented by a series of binary strings, which complete the evolution through selection, crossover and mutation. Firstly, GA enables encoding of variables, and then expresses the search space in the form of encoding. Population size represents the number of every generation of chromosome. In the case of excessively small size, GA will be converged too quickly, often leading to poorer solution owing to insufficient information of population. Fitness function in GA process, also called target function, is used to decide the degree of fitness of a chromosome under an environmental condition, namely, measuring the performance of every chromosome (Holland, 1992; Murthy 1996). Because the parameter space of WBNN in network weight and bias was big, for GA, it would take a long time to calculate the time in analyzing the optimal WBNN network parameters. If GA calculus was generational deficiency, what we found still was not the best parameter solution. Hybrid GA used GA to find the optimal point in advance, and then, according to the present weights and biases, trained the prediction system with the deepest decent in the traditional optimization methods, such as EBP (error back propagation). Thus, the optimal network weight and bias parameter could be obtained and the prediction model of multi-quality characteristics could be more efficient. The optimal prediction model of WBNN was obtained by HGA, achieved through the procedures of executing HGA is simplified as follows.

1. The fitness function was chosen and the fitness function of this paper was expressed by Eq. (4).

2. The initial conditions of GA were set to include the following parameters: the number of chromosomes, the number of evolution, mating rate, mutation rate etc.
3. The weight and bias parameters of WBNN were used as the initial solutions.
4. The solutions of the weight and bias parameters were substituted into WBNN and RMSE of the fitness function was calculated.
5. Proper solutions were chosen to conduct mating.
6. Based on the results of mating, mutation was conducted to produce the next group of candidate solutions.
7. According to the solutions after mutation, the response values were worked out and the best filial generation was produced.
8. The best solution of the filial generation was temporarily set as the optimal solution. If it satisfied the end condition of the algorithm, we would go on with the next step; otherwise, we should go back to step 4.
9. The optimal prediction network model of WBNN process quality was solved.

4.0 Results and Discussions

The orthogonal array used in the study is $L_{27}(3^{10})$ with three repetitions of each quality characteristic for each combination. There are a total of 162 observations in our study. Based on the results of the Taguchi experiment, the data set contained ten input variables (control factors) and two target variables (η). After Taguchi configuration experiment, for the measured values of each experimental combination, the η_i^q of their loop height and wire bonding strength were respectively worked out with the formulae of the nominal-the-better characteristic and the larger-the-better characteristic. The unit was decibel (dB); there into, i was the experimental combination ($i = 1, 2, \dots, 27$), q was the quality characteristic ($q = 1, 2$). The results of Taguchi experiment showed that the maximum value of η in the quality characteristic of loop height was $\eta_{22}^1 = 42.22 \text{ dB}$; the average loop height: $\bar{y}_{22}^1 = 63.67 \text{ mil}$; According to the results of Taguchi experiment, the optimal factor level combination of loop height should be: $A_2 B_2 C_2 D_2 E_1 F_3 G_2 H_2 J_1 K_3$. In addition, for the quality characteristic of wire bonding strength, the maximum η in Taguchi experiment was $\eta_{17}^2 = 15.89 \text{ dB}$, $\bar{y}_{17}^2 = 6.23$. According to the results of Taguchi experiment, the optimal factor level combination of wire bonding strength should be: $A_2 B_3 C_3 D_2 E_1 F_3 G_3 H_1 J_2 K_1$. The results of Taguchi experiment also showed that the loop height of wire bonding didn't accord with the quality characteristic of wire bonding strength in the optimal level combination.

This research normalized the data obtained from the experimental results of Taguchi's orthogonal array and then used them as the training data constructing WBNN network model. The data set containing the total 27 observations of experimental data was divided into 24 observations for the training group and 3 observations for the test group, which would be used to train and construct WBNN network. The WBNN model constructed in this research was shown in Fig. 2; there into, the number of neurons on the input layer was set as 10 process parameters (control factors); there were 6 neurons on the hide layer; in transfer function, sigmoid function was adopted; in addition, there were 6 neurons on output layer, and the first three output values (y_1, y_2 and y_3) were the quality outputs of loop height, while the last three output values (y_4, y_5 and y_6) were the quality outputs of wire bonding strength; the transfer function of output layer was linear function; in error function, the RMSE statistical index of Eq. (4) was used to evaluate the learning quality of network.

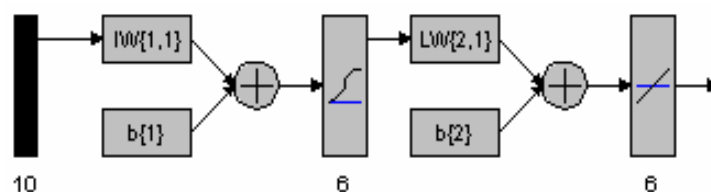


Fig. 2 The WBNN architecture for micro HDD driver IC

After the neural network framework was decided, the training data were input to conduct training.

The training results were shown in Fig. 3 in which the horizontal coordinate stood for the times of learning and the vertical coordinate represented the convergence errors. The convergence value of RMSE had reached 0.11083. When the neural network training had been finished, the test data could be input to confirm the effectiveness of network learning. Table 4 displayed the test results of WBNN model. The error between predictive value and target value inferred by the network was very low, indicating that the constructed WBNN prediction model could fully embody the quality prediction of wire bonding process.

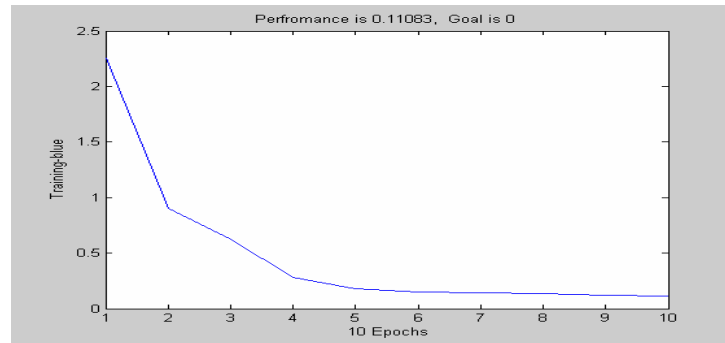


Fig. 3: The Training RMSE for WBNN Model

Table 4: The prediction errors for WBNN models

	Prediction			Target			Prediction Error		
y_1	59.724	62.286	61.894	61.2	62	63	1.476	-0.286	1.106
y_2	60.461	60.286	59.908	60	60	58	-0.461	-0.286	-1.908
y_3	60.700	60.848	59.870	60	61	61	-0.7	0.152	1.13
y_4	1.9315	4.2343	2.5774	2.2	4.33	2.6	0.2685	0.0957	0.0226
y_5	3.8159	2.9706	1.7077	3.6	3	1.6	-0.2159	0.0294	-0.1077
y_6	2.8158	3.4998	2.0787	2.78	3.5	2.1	-0.0358	0.0002	0.0213

The experimental data in this research were obtained by planning each experimental combination and repeating three times based on $L_{27}(3^{10})$ orthogonal arrays, so each combination had 6 experimental data. The purpose was to take the variability of process into consideration so as to make the accuracy of the prediction model constructed by the neural network closer to the actual production process. Additionally, the 10 processes parameter values were respectively 69, 14, 28, 6, 16, 155, 2, 27, 39 and 4. After the process parameter value was input to the neural prediction system, the obtained predictive loop height value and the wire bonding strength value were respectively 60.62 mil and 7.30 gf , the optimal process parameter would be provided to the engineering workers on the scene to execute confirmation experiment. The confirmation experiment value of loop height was 59.61 and the relative error was 1.69%; the confirmation experiment value of wire bonding pull strength was 6.84 gf and the relative error was 6.72%. From the results of experiment, the small relative error showed the optimal parameter value solved in this research could effectively achieve the requirements of quality specifications.

5.0 Conclusions

Because the appearance size of micro HDD driver IC became increasingly thinner, the follow-up packaging process was made even more difficult. Especially in the wire bonding process of CSP package, the insufficient wire bonding strength and weak control of loop height would affect the yield rate of products. In order to satisfy the requirements of quality specifications, such as the low wire bonding height of thin package of 0.65 mm, wire bonding strength etc., this research combined the Taguchi method and hybrid methods of artificial intelligence, used them as the optimal tool in designing parameters, and then constructed a set of the optimal parameter analysis flow and steps. Thus engineers

could quickly obtain the optimal production process parameter with the demand of multi-quality characteristics, and enhance the assembly quality and yield of driver IC of micro HDD.

References

1. Baliga, J. (1998), "Making room for more performance with chip scale packages", *Semiconductor International*, pp. 85-92.
2. Chaudhry, I. and Barez, F. (1998), "Optimization of Wire Loop Height for a Cavity Down Plastic Pin Gird Array Package", *Transactions of the ASME Journal of Electronic Package*, ASME, Vol. 113, pp. 194-200.
3. Chen H. C. (2000), "Study on Wire Bonding Process for Chip Scale Packaging", Thesis, Dept. of Industrial Mechanical Engineering National Cheng Kung University, Taiwan.
4. Chen, J. L. and Lin, Y. C., (2000), "A New Approach in Free Air Ball Formation Process Parameters Analysis", *IEEE Transactions on Electronics Packaging Manufacturing*, Vol. 23 No.2, pp. 115-122.
5. DERRINGER, G. and SUICH, R., (1980), "Simultaneous Optimization of Several Response Variables", *Journal of Quality Technology*, Vol. 12 No.4, pp. 214-219.
6. Goldberg, D. E., (1989), "Genetic algorithms in search, optimization, and machine learning", Reading, MA: Addison-Wesley.
7. Groover, R., Shu, W. K. and Lee, S. S., (1994), "Wire Bond Loop Profile Development for Fine Pitch-Long Wire Assembly," *IEEE Transactions on Semiconductor Manufacturing*, Vol. 7 No.3, pp. 393-399.
8. HOLLAND J. H., (1992), "Adaptation in natural and artificial systems", Ann Arbor, MI: The University of Michigan Press.
9. Hu, S. J., Lim, K. S. and Sou, G. Y. (1995), "Gold Wire Weakening in the Thermosonic Bonding of the First bond," *IEEE Transactions on Components, Packaging, and Manufacturing Technology*, Part A, Vol. 18 No.1, pp. 230-234.
10. Joo, B. S., Choi, N. J., Lee, Y. S., Lim, J. W., Kang, B. H. and Lee, D. D. (2001), "Pattern Recognition of Gas Sensor Array Using Characteristics of Impedance", *Sensors and Actuators B Chemical*, Vol. 77 No.1-2, pp. 209-214.
11. Kim, B. and Park, S., (2001), "An optimal neural network plasma model: a case study", *Chemometrics and Intelligent Laboratory Systems*, Vol. 56, pp. 30-50.
12. Kim, B., Kim, D. W. and Park, G. T. (2005). Prediction of plasma-induced DC bias using polynomial neural network, *Vacuum*, Vol. 79, pp. 111-118.
13. Liu, D. S., Chao, Y. C. and Wang, C. H., (2004), "Study of wire bonding looping formation in the electronic packaging process using the three-dimensional finite element method", *Finite Elements in Analysis and Design*, Vol. 40, pp. 263-286.
14. Lo, Y. L. and Tsao, C. C., (2002), "Integrated Taguchi Method and Neural Network Analysis of Physical Profiling in the Wirebonding Process", *IEEE Transactions on Components and Packaging Technologies*, Vol. 25 No.2, pp. 270-277.
15. Murthy, C. A. and Chowdhury, N., (1996), "In search of optimal clusters using genetic algorithms", *Pattern Recognition Letters*, Vol. 17 No.8, pp. 825-832.
16. Ohno, Y., Ohzeki, Y., Yamashita, T., Iguchi, Y., Katsumata, T. and Arao, Y., (1991), "Development of Ultra-Fine Wire for Fine Pitch Bonding", *Electronic Components and Technology Conference, Proceedings*, 41st, pp. 519-523.
17. Phadke, M. S. (1989), "Quality Engineering Using Robust Design", Prentice Hall, Englewood Cliff, NJ.
18. Raimundo, I. M. and Narayanaswamy, R. (2001), "Simultaneous Determination of Relative Humidity and Ammonia in Air Employing an Optical Fibre Sensor and Artificial Neural Network", *Sensors and Actuators B – Chemical*. Vol. 74 No.1-3, pp. 60-68.
19. Sandro, N., (2000), "Feedforward neural networks for principal components extraction", *Computational Statistics and Data Analysis*, Vol. 33 No.4, pp. 425-437.
20. Schalkoff, R. J., (1997), "Artificial Neural Networks", *McGraw-Hill Companies*, INC.
21. Shu, B. (1992), "Wire Bond Development for High-Pincount Surface-Mount", *42st Electronic Components & Technology Conference*, pp. 890-898.
22. Su, C. T. and Chiang, T. L., (2003), "Optimizing the IC wire bonding process using a neural networks/genetic algorithms approach", *Journal of Intelligent Manufacturing*, Vol. 14, pp. 229-238.
23. Tong, L. I., Su, C. T. and Wang, C. H., (1997), "The optimization of multi-response problems in Taguchi method", *International Journal Quality Reliability Management*, Vol. 14, pp. 367-380.
24. TSAO, C. C. (2000), "The Taguchi Method and Neural Network Analysis in a Loop of Wire Bonding Profile for I.C. Packaging", Thesis, Dept. of Industrial Mechanical Engineering National Chung

Cheng University, Taiwan.

Authors' Background

Dr. Yung-Hsiang Hung is an associate professor in Industrial Engineering and Management at National Chin-Yi Institute of Technology. He received his PhD in Industrial Engineering and Management at National Chiao-Tung University in 2002. His main research interest is in the area of statistical process control and service quality management. His research areas include process capability analysis, semiconductor manufacturing management and process parameters optimization design.

Prof. Mei-Ling Huang is a professor in Department of Industrial Engineering and Management at National Chin-Yi Institute of Technology. She will receive her PhD in Industrial Engineering and Management at National Chiao-Tung University in 2003. Her main research interest is in the area of statistical process control and service quality management. She has published several articles about process capability indices.

Mr. Chin-Huang Chang received the B.S. degree from Yunlin Institute of Technology and the Master degree in Industrial Engineering from Feng Chia University, Taichung, Taiwan. He was previously a research engineer with the System in Package IC products and assembly process in IC packaging of semiconductor industrial. He is currently a manager in Siliconware Precision Industries Co., Ltd. R&D Division. His research interests include Artificial Intelligence, management of technology and innovation, System in Package IC products and process development.